

Thermal, Structural, Morphological and Dielectric Studies of Sol Gel Derived Codoped $\text{SrTiO}_{3-\delta}$

Ramanjeet Kaur^{*1} and Anand K Tyagi²

¹*Department of Applied Sciences, SBSSTC, I. K. Gujral Punjab Technical University, Kapurthala, 144603 (Punjab) India.*

²*Department of Applied Sciences, SBS State Technical Campus, NH-05, Firozpur 152004 (Punjab) India.*

Abstract: Gadolinium and Thulium doped $\text{SrTiO}_{3-\delta}$ i.e. $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Th}_y\text{O}_{3-\delta}$ for $0 \leq x \leq 0.30$ and $0 \leq y \leq 0.05$ have been successfully synthesized using sol gel technique in this work. XRD patterns of the obtained ceramics are found to be sharp and well defined having no impurity phases for all the compositions. The lattice parameter decreases with amount of Gadolinium. Thermal Analysis, XRD, FESEM and EDX studies confirm the formation of $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Th}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) ceramics with required cubic structure. FESEM/EDX analysis revealed that ceramics possess high density with marginal inter-granular porosity. The dielectric studies of the synthesized samples revealed that the synthesized samples possess high dielectric constants, high ac conductivity and low loss factors. The improvement in the dielectric properties of the synthesized samples has been observed with gadolinium and thulium doping.

Key words: Thermal, Structural, morphological, sol gel, codoped $\text{SrTiO}_{3-\delta}$ perovskite

1. Introduction

Energy is the one of the basic requirements for sustainable development. The energy sources used nowadays suffer from many problems like global warming [1], various pollutions, their limited stocks etc. so renewable sources like wind, solar, hydrothermal energy etc were invented but these are dependent on climate conditions and are also less efficient.

Fuel cell is one of the leading options available as efficient and environment friendly technologies that can generate power from renewable fuels like hydrogen etc. A fuel cell, like a battery, can generate electricity from electrochemical reaction. It can produce electricity as long as it is supplied the source of H_2 and O_2 . Solid oxide fuel cells (SOFCs) are better than other fuel cell types like alkaline fuel cell, phosphoric acid fuel cell, molten carbonate fuel cell due to various limitations like requirement of pure fuel, expensive catalyst, corrosive electrolyte, high temperature requirement etc [2-3].

Anode, cathode and electrolyte are the main components of SOFCs. The conventional materials i.e. nickel/copper – yttria stabilized zirconia, rare earth doped ceria etc., used for the fabrication of different components of SOFCs, suffer from the various problems like sulfur poisoning, poor mechanical integrity, carbon deposition and lesser stability in reducing conditions. These problems put a major hurdle in commercializing this futuristic technology. The oxides with perovskite structure have emerged as good alternates as these


can withstand the aforesaid problems. The most widely studied perovskites are Strontium titanates, Lanthanum chromites and their doped forms [4-5]. The doping of $\text{SrTiO}_{3-\delta}$ with various elements i.e. La, Ce, Sm, Gd, Dy, Y, Cu for Sr site and Fe, V, W, Mo, Ta, Nb for Ti site have been investigated by various research groups and enhancement in the ionic conductivity has been reported [6-7].

A number of synthesis routes have been employed to synthesize these perovskite materials in literature but all of them suffer from one or the other problems but sol gel based method offers a clean, contamination free and easy method for synthesizing these materials. In this study, Gd and Tm codoped $\text{SrTiO}_{3-\delta}$ i.e. $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) have been synthesized using sol gel technique and investigated for thermal, structural, micro-structural and elemental composition using DTA/TGA, XRD and FESEM/EDS analysis.

2. Experimental Work

2.1. Synthesis

$\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($x = 0, y = 0$; $x = 0.05, y = 0.005$; $x = 0.1, y = 0.005$; $x = 0.15, y = 0.02$; $x = 0.2, y = 0.02$; $x = 0.25, y = 0.05$; $x = 0.30, y = 0.05$) samples had been synthesized via sol gel method employing titanium tetra isopropoxide $\{\text{Ti}(\text{OC}_3\text{H}_7)_4\}$, strontium acetate $\{\text{Sr}(\text{CH}_3\text{COO})_2\}$, Gadolinium Nitrate $\{\text{Gd}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}\}$ and thulium nitrate penta hydrate $\{\text{Tm}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}\}$; all from Alfa AesarTM, as starting chemicals. The propanol, hydrochloric acid (HCl) and distilled water were used as solvents. In total seven samples had been prepared corresponding to various values of 'x' and 'y' i.e. $x = 0, y = 0$; $x = 0.05, y = 0.005$; $x = 0.1, y = 0.005$; $x = 0.15, y = 0.02$; $x = 0.20, y = 0.02$; $x = 0.25, y = 0.05$ and $x = 0.30, y = 0.05$ and were referred as STO0, STO1, STO2, STO3, STO4, STO5 and STO6 for respectively. The required amounts of raw chemicals were calculated using the metallurgical reaction (1).



Firstly a 6wt% alcoholic solution of titanium dioxide (TiO_2) was prepared using titanium tetra isopropoxide (28wt%) as precursor, hydrochloric acid (13wt%) as catalyst, propanol (58wt%) and distilled water (1wt%) as solvent. A part of propanol was mixed with titanium tetra isopropoxide to form a solution (1) and the remaining amount of propanol, distilled water & HCl were mixed to form a solution (2). Both the solutions (1 & 2) were kept stirring at room temperature for 20 minutes and were then mixed to form the alcoholic solution. The alcoholic solution was stirred at room temperature for 24 hours and then calculated amounts of strontium acetate $\{\text{Sr}(\text{CH}_3\text{COO})_2\}$, $\text{Gd}(\text{NO}_3)_3 \cdot 6\text{H}_2\text{O}$ and $\text{Tm}(\text{NO}_3)_3 \cdot 5\text{H}_2\text{O}$ were added to it to prepare the titania solution. The prepared solution was kept for 2-3 hours at room temperature, as a result of which the destabilized titania solution turned to homogeneous opalescent alcogel. The alcogel was then dried at $\sim 80^\circ\text{C}$ and crushed to obtain the fine powder [8]. The obtained powders were calcined at 600°C and then sintered at 1250°C for 2 hours at heating rate 3°C per minute.

The pellets of the sintered powders were prepared with the help of hydraulic press using PVA solution as binder. The binder was expelled by heating the pellets at 600°C for 1 hour at heating rate of 3°C per minute. The sintering was done before the pellet formation to avoid the pulverization of pellets. All the seven samples were prepared using the aforesaid technique in a single go.

2.2. Characterization

DTA/TGA/DTG analysis of uncalcined STO0 ($x=0, y=0$) and STO3 ($x=0.15, y=0.02$) powders was done under nitrogen atmosphere at heating rate $10^\circ\text{C}/\text{minute}$ using EXSTAR

TG/DTA 6300 instrument. X ray diffraction analysis of the synthesized pellets was done with the help of XPERT-PRO X-RAY diffractometer 0000000011141934 using Cu K α radiation. SEM/EDS analysis of the prepared pellets was carried out using Nova Nano FE-SEM (FEI) for morphological and elemental analysis. The dielectric properties of the sintered the samples were studied with the help of LCR HiTester.

3. Results and Discussion

3.1. Thermal Analysis

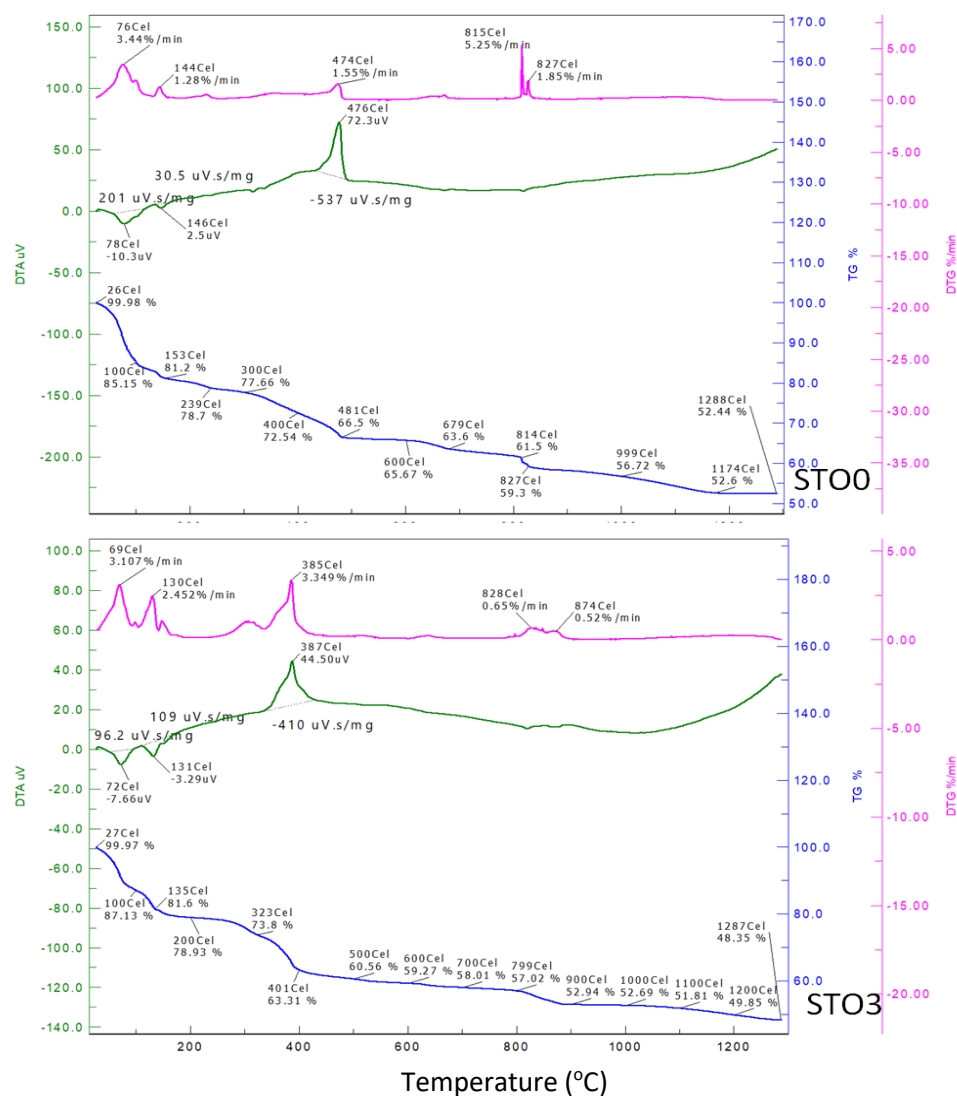


Figure 1. DTA/DTG/TG Curves for Uncalcined Powders of STO0 (x=0, y=0) and STO3 (x = 0.15, y = 0.02) Samples.

DTA/DTG/TG thermograms for uncalcined powders of STO0 (x=0, y =0) and STO3 (x=0.15, y=0.02) samples are shown in Figure 1. Clearly, DTA/DTG/TG curves for both the samples; STO0 and STO3 are almost same. These can be divided mainly in three parts. First part of TG curves corresponds to heavy weight loss from 99% to 78% in the temperature range from 26°C to 239°C with two endothermic peaks at 69°C & 130°C and 78°C & 146°C for STO0 and STO3 respectively. The weight loss and endothermic peaks are due to the evaporation of some remainders of solvents with rise in the temperature.

Second part of TG curve corresponds to weight loss of 17% (STO0) and 22% (STO3) in the temperature range from 240°C to 815°C and exothermic peaks at 385°C and 476°C for STO0 ($x=0$, $y=0$) and STO3 ($x=0.15$, $y=0.02$) respectively. This is due to decomposition of the organic residues present within the samples with increase of the temperature. Third region corresponds to weight loss of approximately 9% in temperature range from 815°C to 1288°C with small endothermic peaks at 815°C and 827°C for STO0 and at 828°C and 874°C for STO3 sample. This region of the curves corresponds to the development of the required $\text{SrTiO}_{3-\delta}$ and $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ phase [8-11].

3.2. XRD Analysis

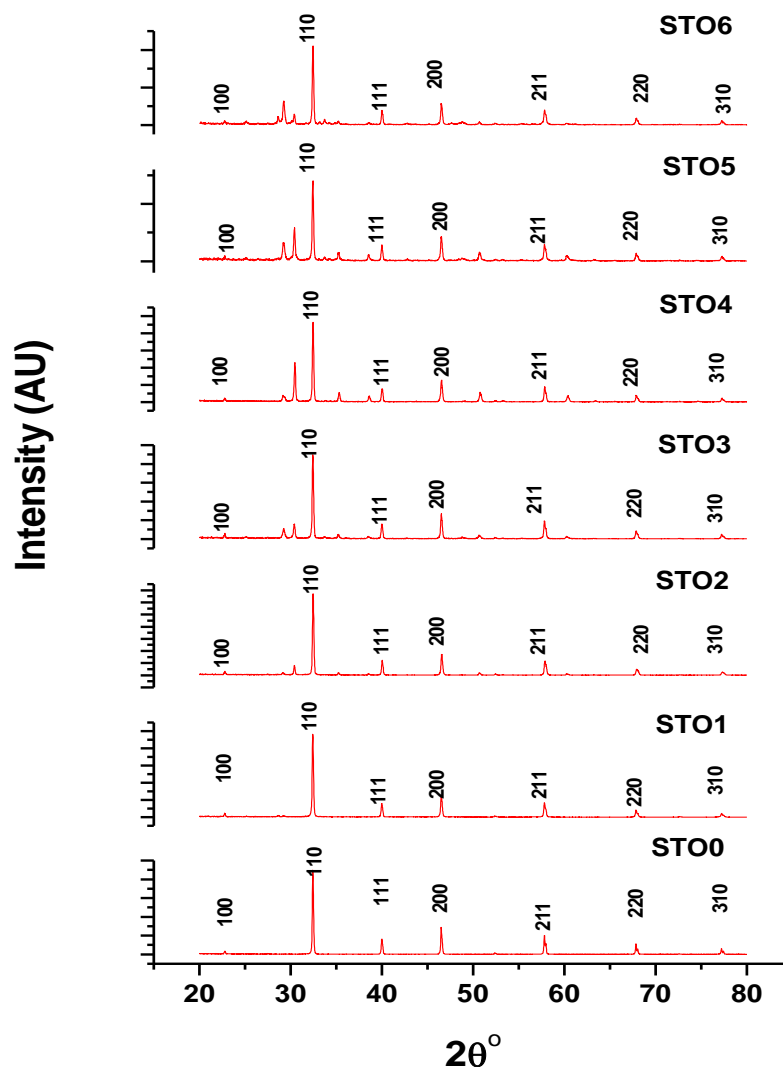


Figure 2. XRD Peak Pattern for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$)

XRD peak patterns of $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) are shown in Figure 2. Clearly, all the XRD peaks are well defined and are indexed on the basis of cubic symmetry of the structure using mathematical method [12]. The XRD patterns observed here are similar to the XRD pattern of SrTiO_3 reported in literature [8]. All the STO samples show nearly identical XRD patterns with no detectable impurity phases indicating the purity of the synthesized ceramics.

The shift of most intense peak (110) for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$; STO samples from pure sample i.e. STO0 with increase in gadolinium content and constant doping amount of thulium is shown in Figure 3. The peaks shift toward the larger angle side with increase in Gd content that may be attributed to intake of relatively smaller ion Gd^{3+} ; ionic radius 107.8 pm, as a replacement of Sr^{2+} ions; ionic radius 132 pm, in the ceramic matrix [6,13].

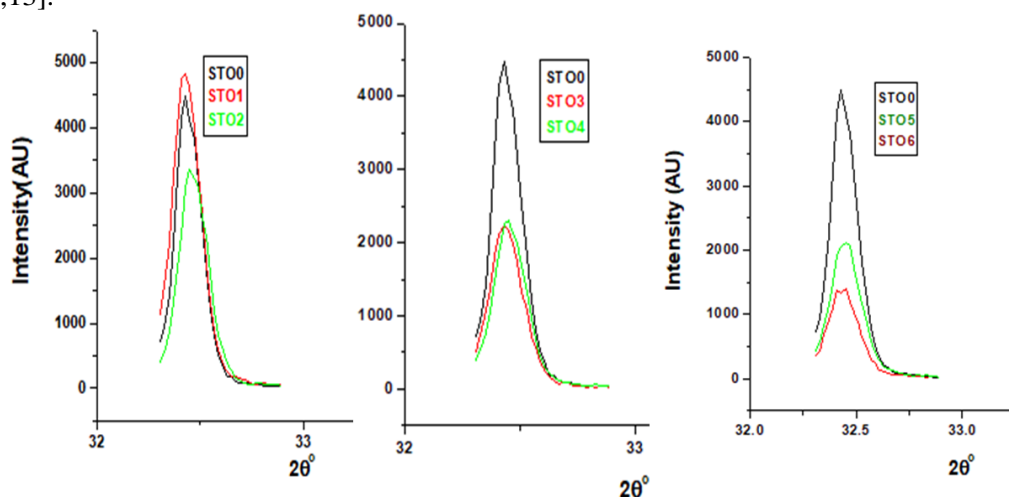


Figure 3. Shift of the Most Intense Peak (110) for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) with Increase in ‘Gd’ Content.

Table 1. Lattice Parameter Values for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$)

Sample Code	x	y	Lattice Parameter (Å)
STO0	0	0	3.9114
STO1	0.05	0.005	3.9022
STO2	0.1	0.005	3.8984
STO3	0.15	0.02	3.9006
STO4	0.2	0.02	3.89975
STO5	0.25	0.05	3.90038
STO6	0.3	0.05	3.89983

The lattice parameters for the synthesized samples were calculated using mathematical method for cubic crystals [12]. The values of lattice parameter ‘a’ for all the doped $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ compounds are included in table 1. The variations of lattice parameter for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) for STO0, STO1 & STO2; STO0, STO3 & STO4 and STO0, STO5 & STO6 are shown in figures 4(a), (b) and (c) respectively. The figures clearly reveal that lattice parameter ‘a’ decreases from STO1 to STO2, STO3 to STO4 and STO5 to STO6; all values smaller than that for STO0; the pure undoped sample. The decrease in the lattice parameter is caused by replacement of Sr^{2+} (132pm) by the smaller rare-earth element Gd^{3+} (107.8pm) [13].

The crystallite sizes for all the synthesized samples were calculated for (110) reflection; the peak with maximum intensity, using the Sherrer’s equation (2). The sherrer’s equation [14] is:

$$d = \frac{k\lambda}{\beta \cos\theta} \quad (2)$$

Here d is crystallite size; k is constant, equal to 0.9, as the particles are assumed to be spherical, ‘λ’ is X-ray wavelength (1.5406 Å), β is FWHM and Θ represents the angle of

diffraction for the peak under consideration. All the doped $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples have crystallite size lying in the range from 46 to 52 nm.

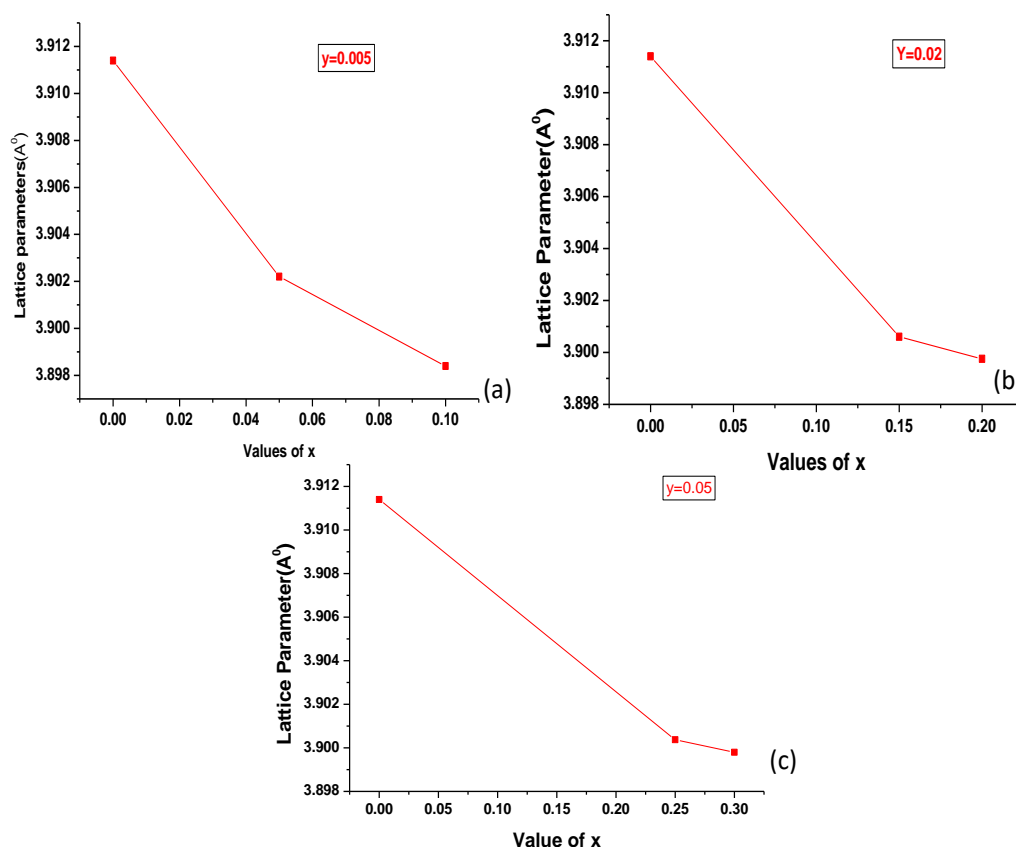


Figure 4. Variation of Lattice Parameter 'a' with 'x' for (a) STO0, STO1 and STO2, (b) STO0, STO3 and STO4 with 'x' and (c) STO0, STO5 and STO6 with 'x'

3.3. FESEM Analysis

The microstructures of all $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$; STO ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) samples as obtained by FESEM are shown in Figure 5. Clearly, all the samples are dense having homogeneous microstructure with well developed small angular grains. The grains have isotropic shapes close to spherical one for STO0 ($x=0$, $y=0$) to STO5 ($x=0.25$, $y=0.05$) ceramics; whereas the grain shape is cuboidal for STO6 ($x=0.30$, $y=0.05$) sample. The grain boundaries for all the prepared samples are smooth and clear having straight edges, well defined corners, faces without any extra phase precipitation. The straight edges confirm the high crystalline nature of the obtained ceramics, similar also revealed by XRD analysis. The synthesized STO samples have good sinterability and the low amount of inter-granular porosity as indicated by few residual and isolated voids present in the micrographs of STO samples. It is worth noting that the low heating rate used in the experiment i.e. $3^\circ\text{C}/\text{min}$ for sintering is favorable to the grain growth.

The microstructures of $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$; STO samples have almost identical features, differing only in grain sizes. The grain sizes for $\text{SrTiO}_{3-\delta}$ samples as obtained from SEM analysis are in the range 407-972 nm, 83-587 nm, 104-750 nm, 234-747 nm, 169-426 nm, 179-618 nm and 43- 407 nm for STO0, STO1, STO2, STO3, STO4, STO5 and STO6 respectively; clearly in the nano range. The grain sizes of the synthesized samples are smaller than reported in the literature; that is normally in the micrometer range for the rare earth doped SrTiO_3 ceramics prepared by other techniques i.e. at high sintering temperature ~ 1300 - 1470°C [6, 15]. The nano size of the synthesized samples may be due

to the fine precursor powders derived from sol-gel method and the low densification sintering temperature.

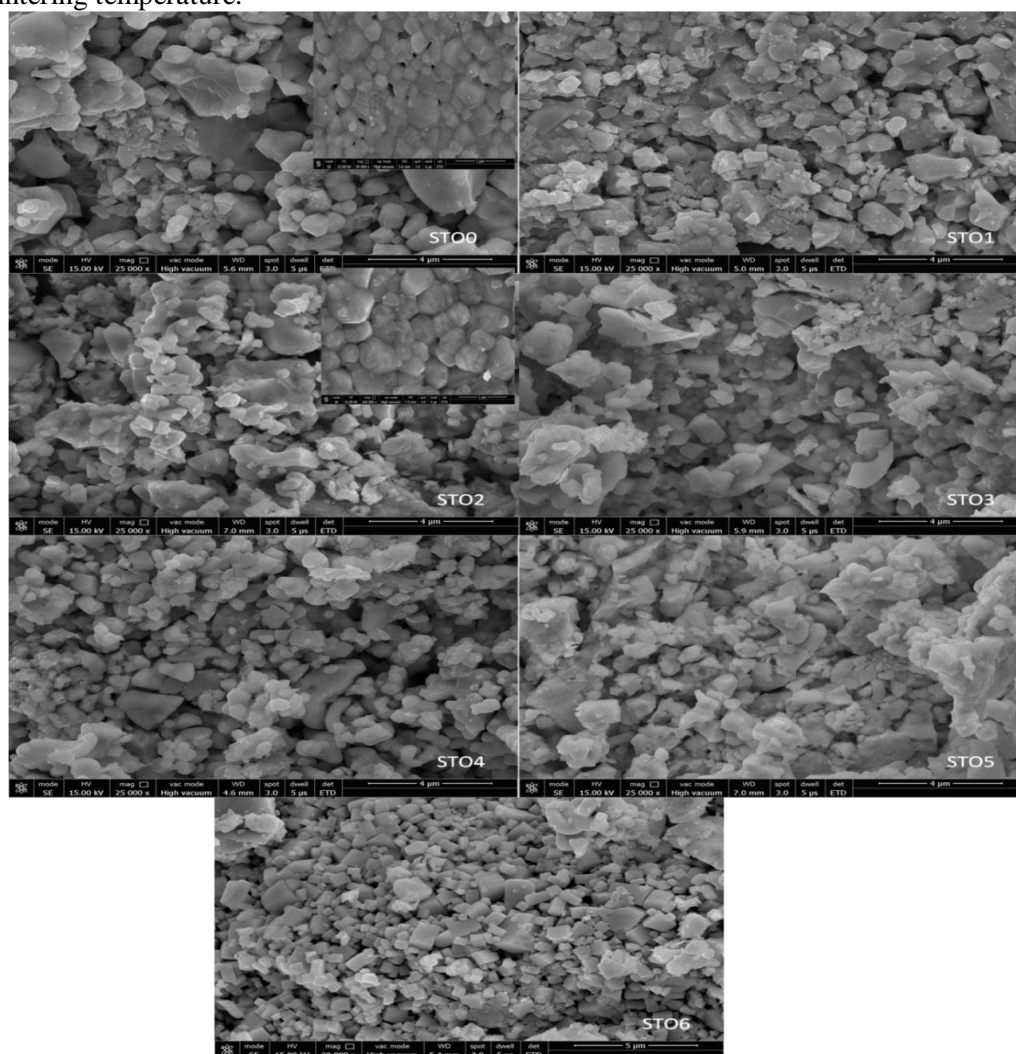


Figure 5. FESEM Image of $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$)

The grain growth in $\text{SrTiO}_{3-\delta}$ has been reported to be highly sensitive to doping amount in literature [6, 16]. Here also, it can be easily realized that increase in Gadolinium and Thulium doping leads to gradual decrease of grain size; with minimum value of grain size for STO6. Thus, the high purity rare earth doped $\text{SrTiO}_{3-\delta}$ materials with high density have been successfully obtained by sol gel process at relatively lower sintering temperature.

3.4. EDX Analysis

From analysis of EDX spectra for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples it was observed that only strontium, titanium and oxygen are present in STO0 ($x=0$, $y=0$), however, along with these elements, gadolinium and thulium are also present in the all other STO compositions. There was no evidence for any other element confirming the purity of the synthesized STO samples. Table 3 includes the atomic ratios of the elements for all the $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) as obtained from EDX analysis, which are almost same as elemental ratio i.e. $\text{Sr} + \text{Gd} : \text{Ti} + \text{Tm} : \text{O} = 1 : 1 : 3$, calculated theoretically.

Table 3. Atomic Ratio of Elements for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) from EDS Analysis

Sample Code	x	y	Sr + Gd	Ti + Tm	O
STO0	0	0	1.26	1	3.29
STO1	0.05	0.005	0.6	1	1.94
STO2	0.10	0.005	0.64	1	2.6
STO3	0.15	0.02	1.03	1	3.08
STO4	0.20	0.02	1.22	1	2.89
STO5	0.25	0.05	0.88	1	2.29
STO6	0.30	0.05	1.04	1	3.25

The atomic composition of all the synthesized $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$; STO samples as obtained from EDX analysis is given in the table 4. It is evident from the data included in the table that amount of gadolinium increases from STO0 to STO6 as expected and that of thulium also increases as required.

Table 4. Atomic Composition of $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ Samples ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) from EDX Analysis

STO	Sr	Gd	Ti	Tm	O
STO0	1.26	0	1	0	3.29
STO1	0.55	0.07	1	0.07	2.08
STO2	0.54	0.14	1	0.06	2.8
STO3	0.92	0.19	1	0.08	3.33
STO4	0.74	0.21	1	0.09	2.51
STO5	0.74	0.41	1	0.11	3.61
STO6	0.93	0.48	1	0.16	3.34

3.5. Dielectric Characterization

The values of dielectric constant (ϵ_r) were determined from the measured values of capacitance using the LCR meter between 30 - 400°C temperatures. The frequency dependence of ϵ_r at 309°C & 400°C is shown in Figure 5 for all the doped samples. The variations of dielectric constant with temperature ranging from 50 to 400°C at frequencies 10 KHz and 100 KHz for all STO compositions are shown in Figure 6. A sharp decrement in ϵ_r values with increase in frequency (<1 kHz) can be observed which may be due to the reason that at low frequency, contribution from electronic, ionic, orientation and space charge polarization exist but at high frequency only electronic polarization or some contribution from ionic polarization [17]. The strong dependence of dielectric constant on frequency up to 1 KHz is evident from Figure6; which is termed as dielectric dispersion [18] and is quite common for dielectric materials. Whereas dielectric constant remains almost constant at frequencies above 1 KHz which is due to the reason that electric dipoles can't follow the fast varying electric field.

The dielectric constant remains almost constant up to a certain temperature and then, increases rapidly with increasing temperature (300–400°C). The space charge polarization arising from the movement of ions and defects in the material may be responsible for this increase [19]. There is no curie peak detected in the whole measurement temperature range [20]. The high values of dielectric constant at room temperature for all the STO samples may be attributed to the presence of all kinds of polarizations at room temperature which can lead to irregular increase in the permittivity [21]. It can be observed that doped STO compounds have larger dielectric constant values in comparison

to undoped SrTiO_3 ; STO0 ceramic sample at all the studied temperatures and frequencies [22].

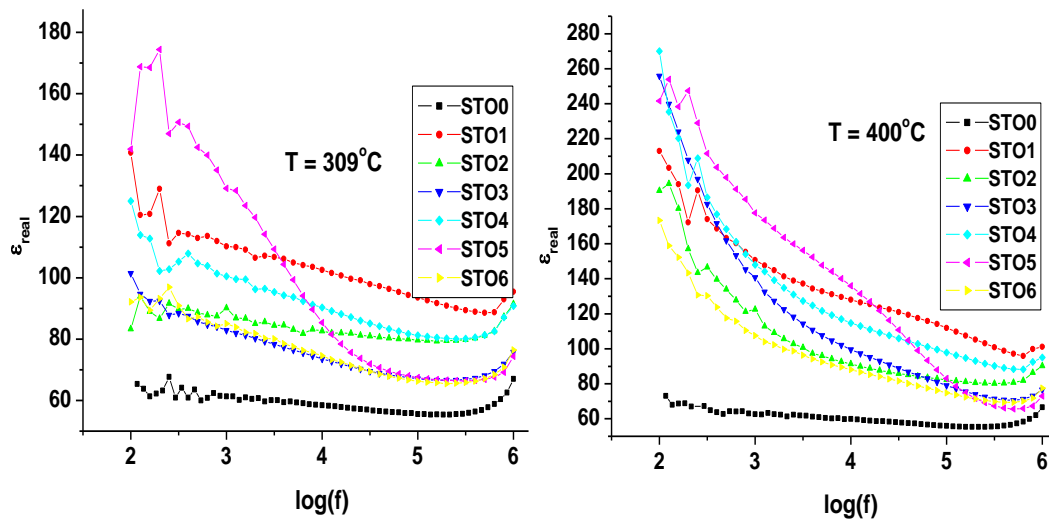


Figure 5. Variation of Dielectric Constant with Frequency at 309°C & 400°C for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) Samples

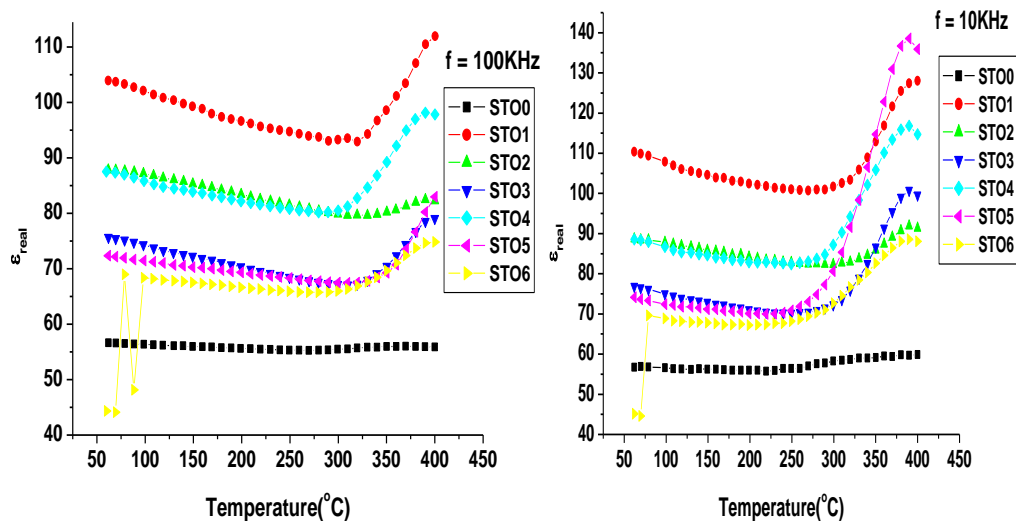


Figure 6. Variation of Dielectric Constant with Temperature at Frequencies 100 KHz and 10 KHz for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) Samples

Figures 7(a) and (b) show the frequency and temperature dependence of imaginary dielectric constant (ϵ'') for doped SrTiO_3 samples respectively. ϵ'' shows the similar trends as that of ϵ' , i.e. increase with temperature and decrease with frequency. There is no loss peak in the whole frequency spectrum of ϵ'' . The values of ϵ'' are high only at low frequencies (below 1 KHz) and at high temperature (300°C to 400°C) owing to the interfacial build up of the free charges either within the sample (Maxwell-Wagner (MW) polarization) [23] or between sample and the electrodes (space-charge polarization). It can be easily observed that doping leads to increase in imaginary component of dielectric constant.

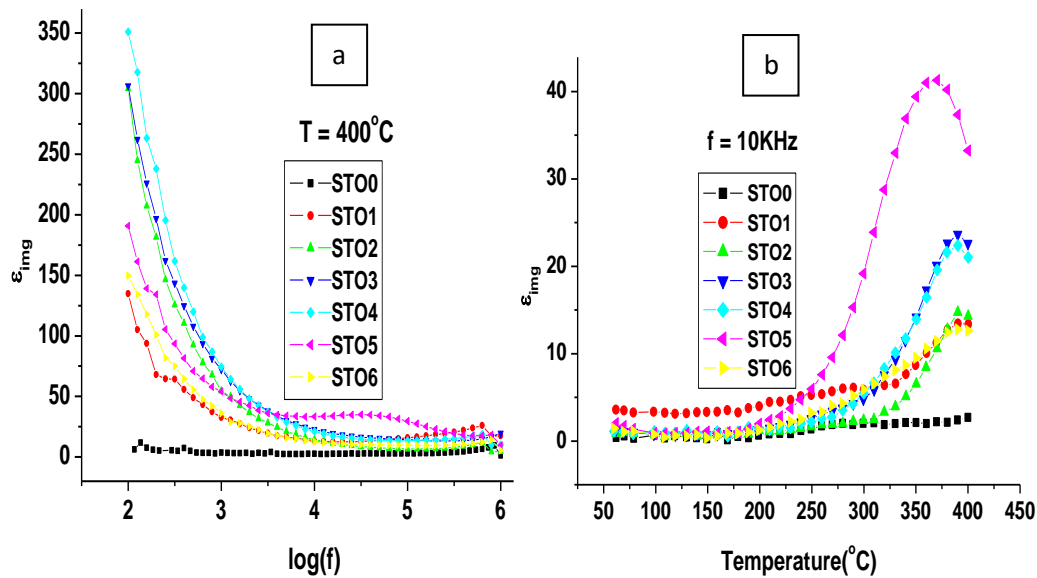


Figure 7. Variation of Imaginary Part of Dielectric Constant (a) with Frequency at 400°C (b) with Temperature at 10KHz for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$)

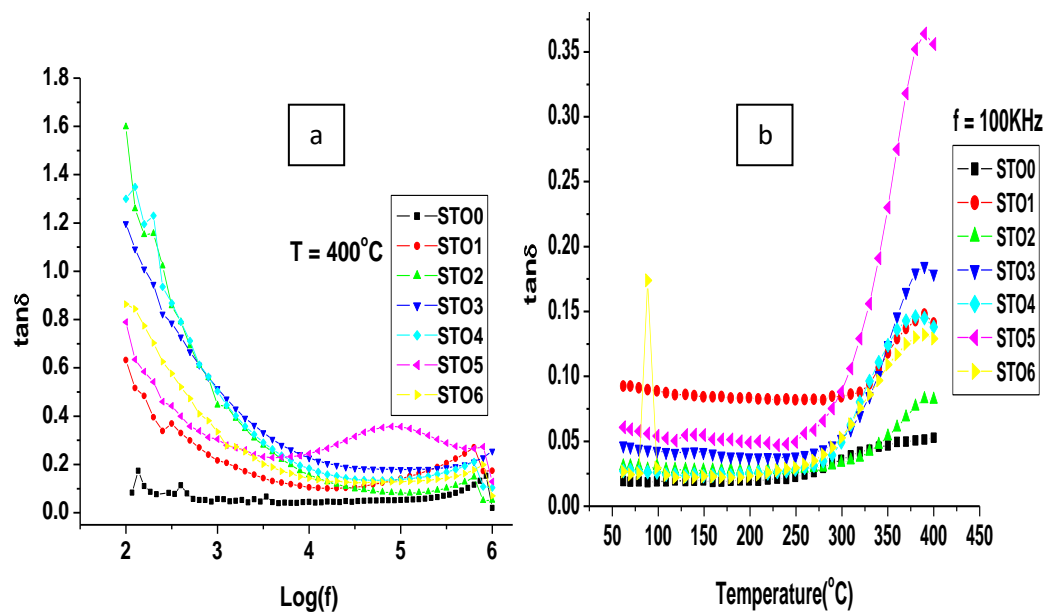


Figure 8. Variation of Dielectric Loss (a) with Frequency at 400°C (b) with Temperature at 100KHz for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) Samples

The variation of loss tangent for the doped samples with frequency at 400°C is shown in Figure 8(a); and Figure 8(b) depicts the dependence of dielectric loss on temperature at frequency 100 KHz from 50 to 400°C . From all these plots, it can be easily observed that $\tan\delta$ values decrease with frequency and increase with temperature. The decrease of dielectric loss with frequency can be explained using the relation (3).

$$\tan \delta \sim \frac{\sigma}{2\pi f} \quad (3)$$

Where $\tan\delta$ is the loss tangent factor, σ is the conductivity and f is the frequency. The increase in frequency is more than the increase in conductivity with frequency [24]. So, loss tangent factor shows a decrease with the increase in frequency within the entire temperature range. The observed enhancement in loss factor values at high temperature

can be due to transportation of thermally energetic ions. The conductivity dominates at high temperatures due to presence of oxygen vacancies and defects created by oxygen loss at high temperature sintering; which leads to increase in loss factor also. In spite of this, the ferroelectric domain walls contribute less at high temperature leading to rise in loss tangent factor. Similar dielectric behavior has been reported in the literature for similar category compounds [20, 22]. The variation trends for the doped samples are approximately identical to that for undoped STO. The increase in loss factor with doping can be observed from Figure 8.

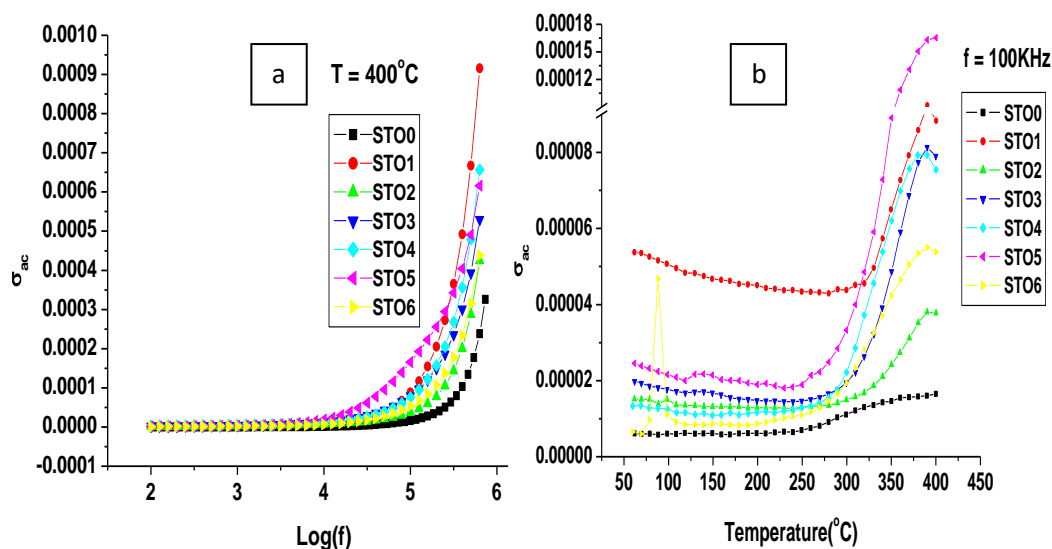


Figure 9. Variation of ac Conductivity (a) with Frequency at Temperature 400°C (b) with Temperature at Frequency 100KHz for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) Samples

Figure 9(a) depicts the frequency dependence of ac conductivity at 400°C and temperature dependence of ac conductivity at 100 KHz frequency for all the doped STO samples is shown in Figure 9(b). It can be easily depicted that ac conductivity is almost constant at lower frequencies; however at higher temperatures and frequencies there is a sharp enhancement in ac conductivity due to the strong hopping mechanism [25].

A plateau in the curves at low frequency and dispersion at high frequencies can be easily observed in the spectra. The conductivity which corresponds to the plateau region, is independent of frequency, and is termed as the DC conductivity. The transportation of the mobile ions due to applied field may be responsible for the observed plateau [26]. The observed trends for doped samples and pure STO0 sample are similar. It can be observed that doping with thulium and gadolinium gives rise to increase in ac conductivity in comparison to undoped STO0 samples. Similar trends were observed for yttrium or lanthanum doped strontium titanate, where conductivity showed an increase with increasing the doping amount [27].

Figure 10(a) shows the variation of the real part of impedance (Z') for all doped STO samples with frequency at 400°C and Figure 10(b) shows the variation of Z' with frequency for pure STO0 sample at various temperatures. The decrement in Z' with frequency as well as with temperature can be easily depicted from the two figures. The value of Z' for all temperatures coincides at high frequency. All the doped samples show behavior similar to pure STO sample. The rise in temperature reduces the barrier which in turn leads to increase in ac conductivity and thus decrement in Z' . The decrease in Z' with rise in temperature is very clear at low frequencies in Figure 10(b); revealing that synthesized materials possesses negative temperature coefficient of resistance.

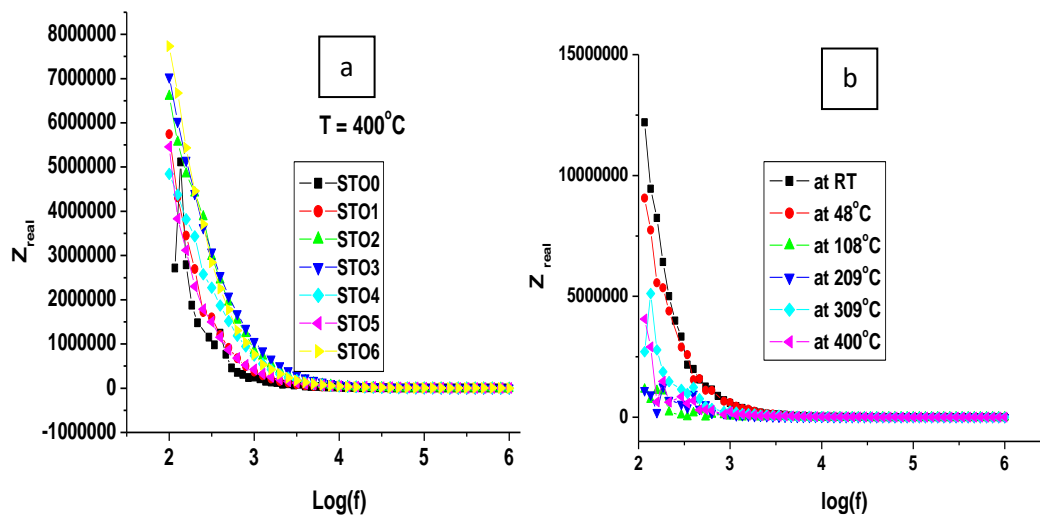


Figure 10. Variation of Real Part of Impedance with Frequency (a) at Temperature 400°C for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) samples (b) at Various Temperatures for Pure SrTiO_3 Sample

Cole-Cole plots can be used to explain the dielectric relaxation phenomenon within the studied frequency range. Figure 11 shows the Cole-Cole plots (Nyquist plots) of doped STO ceramic samples at room temperature and 400°C . All the doped samples almost show the similar plots and radius of semicircle decreases with doping of gadolinium and thulium which shows that resistance decreases with doping. The presence of single depressed semicircle can be easily depicted from the plots for all the studied samples at room temperature as well as at 400°C ; which represents the grain effect in the synthesized material. Furthermore, the increase in temperature leads to decrease in the semicircle radius indicating the decrement in the resistivity. The behavior of doped samples is similar to that of undoped STO sample [28].

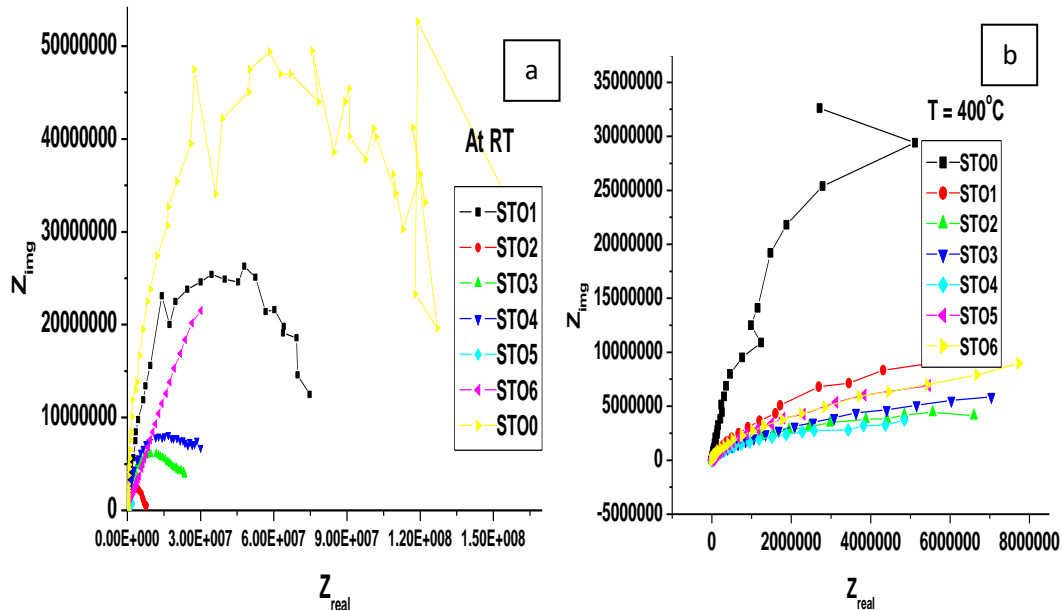


Figure 11. Cole-Cole Plots between Real Part (Z') and Imaginary Part (Z'') of Impedance (a) at Room Temperature (b) at 400°C for $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) Samples

4. Conclusion

In this work, $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ ($0 \leq x \leq 0.30$, $0 \leq y \leq 0.05$) samples have been successfully synthesized using low temperature sol gel technique. The XRD patterns for all the compositions are sharp and well defined having no impurity phases. The lattice parameters decrease with increase in amount of Gadolinium. The microstructures of the synthesized STO samples are homogeneous, less porous and crystalline having nanometric grains. The doping with Gd and Tm further reduces the grain size. EDX analysis suggested that the ratio of strontium, titanium, thulium, gadolinium and oxygen is in close agreement with theoretical values. Thus, thermal, XRD and FESEM/EDX studies reveal the formation of phase pure $\text{Sr}_{1-x}\text{Gd}_x\text{Ti}_{1-y}\text{Tm}_y\text{O}_{3-\delta}$ samples having cubic structure. All the synthesized STO samples possess high dielectric constants, high ac conductivity and low loss factors. The dielectric properties show further enhancement with increase in content of gadolinium and thulium.

Acknowledgements

One of the authors Ms. Ramanjeet Kaur highly acknowledges Inder Kumar Gujral Punjab Technical University, Kapurthala, for its valuable inputs in course of this work. The authors are also very thankful to TEQIP, MHRD/World Bank Project for facilitating the necessary research requirements. Furthermore, authors appreciatively acknowledge IIC, I.I.T. Roorkee, MRC, MNIT Jaipur, Thapar University, Patiala and S B S State Technical Campus, Ferozepur for support in characterization of samples.

REFERENCES

- [1] National Oceanic and Atmospheric Administration, Climate of 2001, Annual review.
- [2] N. Q. Minh, Journal of American Ceramic Society, vol. 76, (1993), pp. 563.
- [3] S. C. Singhal, MRS Bulletin, vol. 25, (2000), pp. 16.
- [4] R. Mukundan, E. L. Brosha and F. H. Garzon, Electrochemical and Solid-State Letters, vol. 7, (2004), pp. A5–A7.
- [5] Z. Cheng, S. Zha and M. Liu, Journal of Electrochemical Society, vol. 153, (2006), pp. A1302– A1309.
- [6] L. Zhang, T. Toshio, N. Okinaka and T. Akiyama, “Thermoelectric Properties of Combustion Synthesized and Spark Plasma Sintered $\text{Sr}_{1-x}\text{R}_x\text{TiO}_3$ (R = Y, La, Sm, Gd, Dy, $0 < x < 0.1$)”, Materials Transactions, vol. 48, no. 8, (2007), pp. 2088-2093.
- [7] M. Tolczyk, S. Molin, M. Gazda and P. Jasinski, “Structural and electrical properties of STF materials for SOFC applications”, Ceramic Materials, vol. 63, no. 1, (2011), pp. 151-156.
- [8] A. Rocca, A. Licciulli, M. Politi and D. Diso, International Scholarly Research Network Ceramics, (2012).
- [9] S. F. P. Donkelaar, R. Ruhl, S. A. Veldhuis, A. Nijmeijer, L. Winnubst and H. J. M. Bouwmeester, “Auto-combustion synthesis of perovskite-type oxides $\text{SrTi}_{1-x}\text{FexO}_{3-\delta}$ ”, pp. 8-9.
- [10] B. Li, C. Wang, W. Liu, Y. Zhong and R. An, Materials Letters, vol.75, (2012), pp. 207–210.
- [11] S. Ueno, K. Nakashima, Y. Sakamoto and S. Wada, Nanomaterials, vol. 5, (2015), pp. 386-397.
- [12] Laboratory Module, Indexing X-Ray Diffraction Patterns.
- [13] R. D. Shannon, Acta Crystallographica, vol. A 32, (1976), pp. 751–767.
- [14] B. D. Cullity, “Elements of X-Ray Diffraction”, Addison-Wesley, 2nd edition, (1978).
- [15] H. C. Wang, W. C. Lei, W. B. Su, J. Liu, Y. Sun, H. Peng and L. M. Mei, Journal of American Ceramic Society, vol. 94, (2011), pp. 838–842.
- [16] M. V. Makarova, A. Artemenko, J. Kopecek, F. Laufek, P. Zemenovaa, V. A. Trepakov and A. Dejnekaa, Scripta Materialia, vol. 116, (2016), pp. 21–25.
- [17] A. Verma, O. P. Thakur, C. Prakash, T. C. Goel and R. G. Mendiratta, “Temperature dependence of electrical properties of nickel– zinc ferrites processed by the citrate precursor technique”, Material Science and Engineering B, vol. 116, no. 1, (2005).
- [18] T. Badapanda, R. K. Harichandan, A. Mishra and S. Anwar, “Relaxor ferroelectric behavior of $\text{BaBi}_4\text{Ti}_4\text{O}_{15}$ aurivillius ceramic”, Journal of Advanced Dielectrics, vol. 3, no. 2, (2013), pp. 1350013.
- [19] P. Abhijit and B. Amitabha, “Structural, dielectric and electrical properties of lithium silicate ceramics: A comparative study”, Journal of Material Science: Materials in Electronics, vol. 24, (2013), pp. 1855–1862.
- [20] W. Li, Z. Ma, L. Gao and F. Wang, “Preparation and Electrical Properties of $\text{La}_{0.9}\text{Sr}_{0.1}\text{TiO}_{3+\delta}$ ”, Materials, vol. 8, (2015), pp. 1176-1186.

- [21] A. Ray, B. Behera, T. Basuy, S. Vajandarz, S. K. Satpathy and Nayak, "Modification of structural and dielectric properties of polycrystalline Gd-doped BFO-PZO", *Journal of Advanced Dielectrics*, vol. 8, no. 5, (2018), pp. 1850031.
- [22] S. K. Rout, S. Panigrahi and J. Bera, "Characterization of Ni-doped SrTiO₃ ceramics using impedance spectroscopy", *Indian Journal of Pure & Applied Physics*, vol. 42, (2004), pp. 741-744.
- [23] S. Kumar and K. B. R. Varma, "Relaxor behavior of BaBi₄Ti₃Fe_{0.5}Nb_{0.5}O₁₅ ceramics", *Solid State Communications*, vol. 147, (2008), pp. 457-460.
- [24] M. A. White, "Physical Properties of Materials", CRC Press: Boca Raton, FL, USA, (2011).
- [25] K. C. B. Naidu, T. S. Sarmash and T. Subbarao, "Synthesis and Characterization of Mn doped SrTiO₃ ceramics", *International Journal of Engineering Research & Technology*, vol. 3, no. 1, (2014).
- [26] T. Badapanda, R. K. Harichandan, A. Mishra and S. Anwar, "Frequency and temperature dependence behaviour of impedance, modulus and conductivity of BaBi₄Ti₄O₁₅ Aurivillius ceramic", *Processing and Application of Ceramics*, vol. 8, no. 3, (2014), pp. 145-153.
- [27] J. Karczewski, B. Riegel, M. Gazda, P. Jasinski and B. Kusz, "Electrical and structural properties of Nb-doped SrTiO₃ ceramics", *Journal of Electroceramics*, vol. 24, (2010), pp. 326-330.
- [28] S. Sahoo, U. Dash, S. K. S. Parashar and S. M. All, "Frequency and temperature dependent electrical characteristics of CaTiO₃ nano-ceramic prepared by high-energy ball milling", *Journal of Advanced Ceramics*, vol. 2, no. 3, (2013), pp. 291-300.